

Product Type: **FABSHIELD 21B**
 Classification: **E71T-11**
 Specifications: **AWS A5.20-2005; ASME SFA5.20**
 Diameter Tested: **.035"; 3/32"**
 Date Tested: **11/13/07**
 Date Generated: **11/15/2007**

This is to certify that the product named above and supplied on the referenced order number is of the same classification, manufacturing process, and material requirements as the material which was used for the test that was concluded on the date shown, the results of which are shown below. All tests required by the specifications shown for classification were performed at that time and the material tested met all requirements. It was manufactured and supplied by the Quality System Program of Hobart Brothers, which meets the requirements of ISO9000, ANSI/AWS A5.01, and other specification and Military requirements, as applicable.

Test Settings

Shielding Medium	Amps / Polarity	Volts	WFS in/min (m/min)	ESO in(mm)	Preheat F(C)	Interpass F(C)	Travel Speed in/min(cm/min)
SELF SHIELDING	270 / DCEN	21	50 (1.3)	3/4 (19)	70(21)	300(149)	6 (15.2)
SELF SHIELDING	200 / DCEN	18	250 (6.4)	1/2 (13)	70(21)	300(149)	8 (20.3)


Mechanical Properties - Tensile

Shielding Medium	Ref. No.	Testing Conditions	Ult. Tensile Strength psi (MPa)	Yield Strength psi (MPa)	Elong.% in 2"
SELF SHIELDING	PA5928	Aged 48 Hrs 200F	95,000 (654)	70,000 (481)	20
SELF SHIELDING	PA5717	Aged 48 Hrs 200F	94,000 (646)	67,000 (465)	22

Ref.No.	Radiographic Inspection	Fillet Weld Test					
PA5928	Conforms	Horizontal :		Overhead :	Conforms	Vertical :	Conforms
PA5717	Conforms	Horizontal :		Overhead :		Vertical :	

Chemical Analysis

Shielding Medium / Ref. No	C	Mn	P	S	Si	Cu	Cr	V	Ni	Mo	Al	Ti	Nb	Co	B	W	Sn	Fe	Sb	N	Mg	Zn	Be
SELF SHIELDING / CA58158	0.31	0.37	0.008	0.004	0.18	0.06	0.04	< .01	0.02	0.01	1.69												
SELF SHIELDING / PA5928	0.27	0.49	0.009	0.004	0.19	0.07	0.03	< .01	0.02	0.01	1.56												

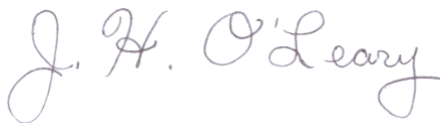

Joe O'Leary, Manager, Quality Assurance



Melvin Seitz, Quality Manager

Certification and Limited Warranty - Data for the above supplied product are those obtained when welded and tested in accordance with the above specification. All tests for the above classification were satisfied. Other tests and procedures may produce different results. Hobart Brothers produces welding consumables under continuing quality assurance programs audited and approved by the American Bureau of Shipping ("ABS").