

Product Type: FABSHIELDXLR-8  
 Classification: E71T-8JH8  
 Specifications: AWSA5.20-2005;ASMESFA5.20  
 Diameter Tested: 1/16";5/64"  
 Date Tested: 12/13/07  
 Date Generated: 10/17/2008

This is to certify that the product named above and supplied on the referenced order number is of the same classification, manufacturing process, and material requirements as the material which was used for the test that was concluded on the dates shown, the results of which are shown below. All tests required by the specifications shown for classification were performed at that time and the material tested met all requirements. It was manufactured and supplied by the Quality System Program of Hobart Brothers, which meets the requirements of ISO 9000, ANSI/AWSA 5.01, and other specification and Military requirements, as applicable.

### Test Settings

Shielding Medium	Amps/Polarity	Volts	WFS in/min(m/min)	ESO in (mm)	Preheat F (C)	Interpass F (C)	Travel Speed in/min(cm/min)
SELF SHIELDING	230/DCEN	22	205(5.2)	1(25)	60(16)	300(149)	8(20.3)
NONE	300/DCEN	23	205(5.2)	1 1/4(25)	60(16)	300(149)	6(15.2)

### Mechanical Properties-Tensile

Shielding Medium	Ref.No.	Testing Conditions	Ult.Tensile Strength psi (MPa)	Yield Strength psi(MPa)	Elong.%in2"
SELF SHIELDING	PA4974	Aged 48 Hrs 200F	89,000(616)	69,000(476)	26
NONE	PA6712	Aged 48 Hrs 220F	79,000(545)	66,000(453)	27

### Mechanical Properties-Impact

Shielding Medium	Ref.No.	Testing Conditions	Temp.F(C)	Individuals ft.lb.(J)	Avg.ft.lb.(J)	Type
SELF SHIELDING	PA4974	As Welded	-40(-40)	30,39,35(41,53,47)	35(47)	Charpy-V-Notch
NONE	PA6712	As Welded	-40(-40)	32,35,33(43,47,45)	33(45)	Charpy-V-Notch


Ref.No.	Radiographic Inspection	Fillet Weld Test			
PA4974	Conforms	Horizontal:	Overhead:	Conforms	Vertical: Conforms
PA6712	Conforms	Horizontal:	Overhead:	Conforms	Vertical: Conforms

### Chemical Analysis

Shielding Medium/Ref.No	C	Mn	P	S	Si	Cu	Cr	V	Ni	Mo	Al	Ti	Nb	Co	B	W	Sn	Fe	Sb	N	Mg	Zn	Be
NONE/CA50564	0.20	0.49	0.005	0.005	0.16						0.43												
NONE/PA6712	0.19	0.53	0.008	0.009	0.18						0.79												

### Diffusible Hydrogen Collected per AWSA 4.3

NONE	7.8ml/100g of weld metal for 5/64 inch diameter
NONE	6.0ml/100g of weld metal for 1/16 inch diameter

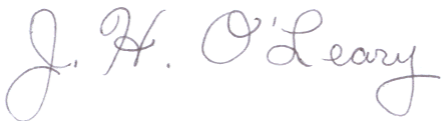

Joe O'Leary, Manager, Quality Assurance



Melvin Seitz, Quality Manager

Certification and Limited Warranty-Data for the above supplied product are those obtained when welded and tested in accordance with the above specification. All tests for the above classification were satisfied. Other tests and procedures may produce different results. Hobart Brothers produces welding consumables under continuing quality assurance programs audited and approved by the American Bureau of Shipping ("ABS").