

Tube-Alloy 255-O

DESCRIPTION:


Tube-Alloy 255-O is a self-shielded, flux-cored wire that deposits an extra high chromium carbide alloy steel. It can be used to overlay surfaces subjected to extremely severe abrasion. It can also be used where high temperature (up to 1250°F) wear resistance is required. Tube-Alloy 255-O is designed for overlay on carbon, low alloy, or austenitic manganese base metals or can be used over a weld metal base of Tube-Alloy Build-Up O, 218-O or AP-O.

Stress-relief cracking will readily occur with this product. This cracking is not detrimental to the wear properties of the deposit and provides some degree of stress relief for the weld metal. Faster cooling rates result in a finer, more uniform stress relief cracking pattern.

OPERATIONAL CHARACTERISTICS:

Tube-Alloy 255-O has a steady arc with a globular transfer. Spatter and noise levels are minimal. The minimal slag coverage allows it to operate well in automatic applications without slagging between passes. Out-of-position welding is limited to a horizontal shelf technique. Tube-Alloy 255-O can be run submerged arc by using with a neutral flux.

RELATIVE WEAR RESISTANCE:

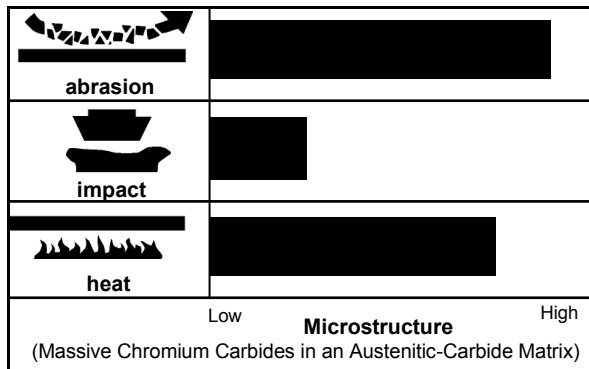

TYPICAL WELD METAL PROPERTIES* (Chem Pad):

Weld Metal Analysis

Carbon (C)	5.30
Manganese (Mn)	1.60
Silicon (Si)	0.80
Chromium (Cr)	28.5
Iron (Fe)	Bal.

TYPICAL MECHANICAL PROPERTIES* (As Welded):

	Number of Layers	As Deposited on	
		1020 Steel	Mn Steel
Hardness	1	54 Rc	48 Rc
	2	56 Rc	50 Rc
	3	58 Rc	53 Rc
Abrasion resistance	Excellent		
Impact resistance	Poor		
Nonmachinable:	Grinding is Difficult		
Cannot be flame cut			
Deposit will relief check cracks readily			
Maintains hot hardness to 1250°F			
Thickness should be limited to three layers maximum			

*The information contained or otherwise referenced herein is presented only as "typical" without guarantee or warranty, and Hobart Brothers Company expressly disclaims any liability incurred from any reliance thereon. No data is to be construed as a recommendation for any welding condition or technique not controlled by Hobart Brothers Company.

Tube-Alloy 255-O

RECOMMENDED OPERATING PARAMETERS:

Diameter		Type of Power	Stick-Out		Optimum Amps	Volts	Deposition Rate	
Inches	mm		Inches	mm			Amps	lb./hr.
1/16	1.6	DCEP	1 -1-1/2	25 - 28	225 - 275	23 - 25	200	6
					275 - 350	24 - 27	250	10
					350 - 400	26 - 29	300	14
7/64	2.8	DCEP	1-1/2 - 2	38-51	350 - 400	24 - 27	300	11
					400 - 450	26 - 29	350	14
					450 - 500	28 - 32	400	18

Start with **middle ranges** and adjust accordingly. Higher amperages will increase deposition rate, dilution, and heat input to base metal, increasing voltage will widen and flatten bead profile, but excessive voltage will result in porosity. Too much electrical stick-out may result in increased spatter, too little may result in internal porosity.

AVAILABLE DIAMETERS AND PACKAGES:

Diameter		25-lb. Spool	60-lb. Coil	100-lb. Auto-Pak	500 lb. Auto-Pak
Inches	mm				
1/16	1.6	S605519-029	S605519-062	--	--
7/64	2.8	--	S605539-062	S605539-266	S605539-097

APPLICATIONS:

Similar to Tube-Alloy 240-O where additional abrasion resistance is required.

- Ammonia Knives
- Augers
- Bucket Teeth and Lips
- Bulldozer End Bits and Blades
- Cement Chutes
- Coal Feeder Screws
- Coal Pulverizer Hammers, Rolls and Table
- Coke Chutes
- Coke Pusher Shoes
- Conveyer Screws
- Crusher Jaws and Cones
- Cultivator Chisels and Sweeps
- Dragline Buckets
- Dredge Cutter Heads and Teeth
- Dredge Pump Inlet Nozzle and Side Plates
- Fan Blades
- Grizzly Bars and Fingers
- Gyrotory Crusher Mantles and Cones
- Manganese Pump Shells
- Muller Tires
- Ore and Coal Chutes
- Pipeline Ball Joints
- Pug Mill Paddles
- Ripper Shanks
- Road Rippers
- Scraper Blades
- Screw Conveyors
- Sheepsfoot Tampers
- Sizing Screens
- Subsoiler Teeth

TECHNICAL QUESTIONS? For technical support of Hobart Filler Metals products, contact the Applications Engineering department by phone toll-free at 1-800-532-2618 or by e-mail at Applications.Engineering@hobartbrothers.com

CAUTION:

Consumers should be thoroughly familiar with the safety precautions on the warning label posted in each shipment and in the American National Standard Z49.1, "Safety in Welding and Cutting," published by the American Welding Society, 8669 NW 36th St., Miami, FL 33166 (can also be downloaded online at www.aws.org); OSHA Safety and Health Standards 29 CFR 1910 is available from the U.S. Department of Labor, Washington, D.C. 20210

Material Safety Data Sheets on any Hobart Brothers Company product may be obtained from Hobart Customer Service or at www.hobartbrothers.com.

Because Hobart Brothers Company is constantly improving products, Hobart reserves the right to change design and/or specifications without notice.

Hobart and Tube-Alloy are registered trademarks of Hobart Brothers Company, Troy, Ohio.

Revision Date: 150810 (Replaces 100617)
260-I, INDEX

